

# Influence of alloying (Cr, Fe, Ni) on the corrosion resistance of layers formed by electron-beam processing

Evdokiya Bushueva <sup>a\*</sup> , Evgeniy Turlo <sup>a</sup>, Evgeniya Kladieva <sup>a</sup>,  
Veronica Sulyaeva <sup>b</sup> , Elizaveta Pukhova <sup>a</sup>

a: Faculty of Mechanical Engineering and Technologies, Novosibirsk State Technical University, Novosibirsk 630073, Russia

b: Nikolaev Institute of Inorganic Chemistry SB RAS, Novosibirsk 630090, Russia

\* Corresponding author: [bushueva@corp.nstu.ru](mailto:bushueva@corp.nstu.ru)

This paper belongs to the CTFM'22 Special Issue: <https://www.kaznu.kz/en/25415/page>.

Guest Editors: Prof. N. Uvarov and Prof. E. Aubakirov.

© 2022, the Authors. This article is published in open access under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).



## Abstract

The paper presents the results of comparative analysis of the properties of coatings based on chromium, nickel and iron borides. The alloy obtained in the process of electron-beam surfacing of the powder mixture “amorphous boron – 10 wt.% chromium” has the best properties. This is explained by the structures, fine chromium borides Cr<sub>2</sub>B and complex iron borides (Fe, Cr)<sub>2</sub>B, distributed in the austenitic matrix. The material modified in this way in a nitric acid solution corrodes at a rate of 0.02 mm/year. In sulfuric acid, its corrosion rate is 0.81 mm/year.

## Key words

stainless steel  
corrosion resistance  
surface modification  
electron beam  
metal borides

Received: 27.06.22

Revised: 21.07.22

Accepted: 01.08.22

Available online: 12.08.22

## Key findings

- The greatest positive effect was obtained in the process of electron-beam surfacing of the powder mixture of "amorphous" boron and 10 wt.% chromium.
- The corrosion resistance of chromium-modified layers is related to the morphology of the chromium borides Cr<sub>2</sub>B formed during surfacing.
- This result is novel, and the developed material can be recommended as a protective corrosion-resistant layer for products made of structural chromium-nickel steels.

## 1. Introduction

Chemical, oil and gas, power industries and mechanical engineering are among the strategically important industries in modern Russia. Chromium-nickel austenitic steels are widely used due to their high corrosion resistance and machinability for manufacture of critical structures in these industries [1, 2]. However, one of the problems limiting the use of chromium-nickel austenitic steels as materials for tribological applications is their low resistance to abrasive wear [3–5]. A rational solution that makes it possible to significantly improve these characteristics is the application of wear-resistant protective layers to wear surfaces by high-energy methods, for example, non-vacuum electron beam surfacing (EB) of powder mixtures [6–8]. However, increasing the strength of the surface layers can lead to a loss of the corrosion resistance of the material [9, 10]. Therefore, the determination of the influence of alloying elements on the oxidation resistance

during surface hardening of stainless steels is an urgent task of modern industry [11–13].

## 2. Materials and methods

Surfacing of powder mixtures was carried out at Budker Institute of Nuclear Physics of Siberian Branch Russian Academy of Sciences (BINP SB RAS) at the industrial electron accelerator ELV-6. Processing was carried out in the scanning mode according to the following parameters: electron beam energy – 1.4 MeV; maximum power – 100 kW; scan rate – 5 Hz; speed of sample movement relative to the beam – 10 mm/s; beam current – 23 mA [14–16]. Amorphous boron (40 wt.%), Fe, Ni, Cr (10 wt.%), MgF<sub>2</sub> (wt.50%) were used as a deposited powder mixture [17–19]. The tests to determine the corrosion resistance of materials were carried out by anodic etching in inhibited sulfuric acid and in an oxidizing environment with weight

loss control [20–22]. Unmodified steel 12X18H9T was chosen as a standard [8].

### 3. Results and Discussion

Corrosion resistance was evaluated by the gravimetric method by measuring the mass loss of samples during chemical reactions. The corrosion rate of materials was calculated according to the standard method ISO 11845:1995 "Corrosion of metals – General principles for corrosion testing".

It was established that the samples obtained using chromium as a wetting component have oxidation resistance 1.75 times higher than the reference material (steel 12Kh18N9T) [23–25]. The resistance of the nickel-modified materials is 1.4 times higher than that of the standard. The corrosion rate increased 1.3 times when using iron as a wetting component.

The results of the corrosion resistance analysis are shown in Figure 1.

The increase in the corrosion resistance of the analyzed materials is explained by the favorable effect of chromium and nickel, as well as the formation of chemically resistant chromium and iron borides in the surface layers [8, 26]. Structural features of the surface of the samples after corrosion tests were analyzed using the method of scanning electron microscopy.

The resulting images reflect the nature of the impact of acids on materials deposited by an electron beam [26]. One of the characteristic features recorded by scanning electron microscopy is etching of the interboride space (Figure 2). One of the reasons for corrosion resistance of chromium-modified layers is related to the morphology of the chromium borides  $Cr_2B$  formed during the surfacing. It is assumed that elongated borides contribute to the development of corrosion processes in the alloy to a lesser extent.


Figure 3 shows the data characterizing the mass loss of the samples obtained in the process of surfacing amorphous boron with different wetting components (Cr, Fe, Ni).

### 4. Conclusions


The creation of boron-containing layers on workpieces made of chromium-nickel steel by the EB method makes it possible to maintain or increase the level of corrosion resistance in boiling concentrated nitric acid and inhibited sulfuric acid. The greatest positive effect was recorded in the study of the samples obtained in the process of electron-beam surfacing of the powder mixture of "amorphous boron – 10 wt.% chromium". The layer modified in this way in a nitric acid solution corrodes at a rate of 0.02 mm/year (the corrosion rate of steel 12X18H9T is 0.05 mm/year). In sulfuric acid, the corrosion rate of the deposited material was 0.81 mm/year, which is 1.7 times lower compared to 12Kh18N9T steel (1.4 mm/year). The developed material can be recommended as a protective corrosion-resistant layer for products made of structural chromium-nickel steels.

### Supplementary materials


No supplementary materials are available.

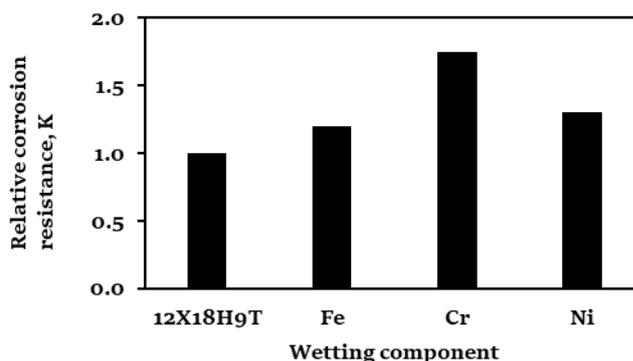

**Figure 1** Relative corrosion resistance of 12Kh18N9T steel and samples obtained by surfacing amorphous boron and 10 wt.% wetting components (Fe, Cr, Ni).

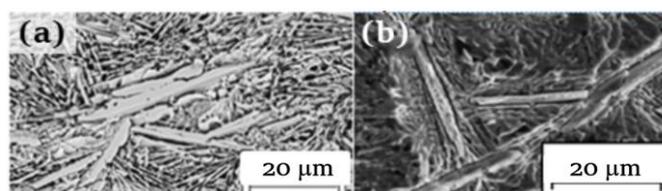

**Figure 2** Surface morphology of alloyed layers (surfacing of amorphous boron and 10 wt.% chromium,  $I = 23$  mA) after corrosion tests in inhibited sulfuric acid (a) and (b) nitric acid.

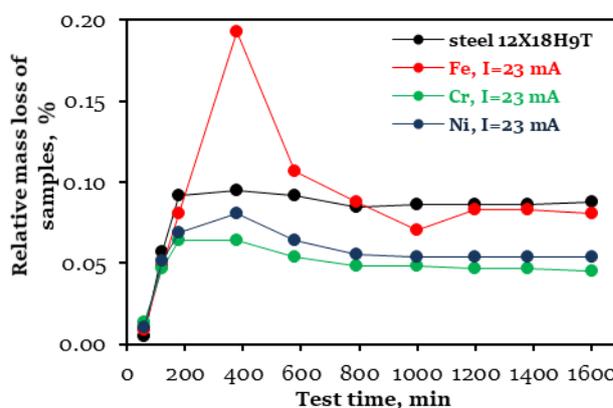

**Figure 3** The nature of the change in the relative mass loss of samples obtained by non-vacuum electron beam surfacing of amorphous boron with various wetting components, from the time of exposure to nitric acid. Surfacing current is 23 mA.

### Funding

The work on microscopic characterization of samples was supported by the Ministry of Science and Higher Education of the Russian Federation, project No. 121031700314-5. The work is done in accordance to TP\_XXT 1-22.

### Acknowledgments

The studies were carried out on the equipment of the Central Collective Use Center "Structure, mechanical and physical properties of materials" of NSTU (No. 13.TsKP.21.0034, 075-15-2021-698).

## Author contributions

Conceptualization: E.B., E.T.  
 Data curation: E.B., E.T.  
 Formal Analysis: E.B., E.T., E.K., E.P., V.S.  
 Funding acquisition: E.B.  
 Investigation: E.B., E.T., E.K., E.P.  
 Methodology: E.B., E.T.  
 Project administration: E.T.  
 Resources: E.T.  
 Software: E.B.  
 Supervision: E.T.  
 Validation: E.B., E.T.  
 Visualization: V.S.  
 Writing – original draft: E.B., E.T.  
 Writing – review & editing: E.B., E.T.

## Conflict of interest

The authors declare no conflict of interest.

## Additional information

### Author IDs:

Evdokiya Bushueva, Scopus ID [25627090600](https://scopus.com/authid/detail.url?authorID=25627090600);  
 Evgeniy Turlo, Scopus ID [57220026913](https://scopus.com/authid/detail.url?authorID=57220026913);  
 Veronica Sulyaeva, Scopus ID [12141245300](https://scopus.com/authid/detail.url?authorID=12141245300).

### Websites:

Novosibirsk State Technical University, <https://en.nstu.ru>;  
 Nikolaev Institute of Inorganic Chemistry SB RAS,  
<http://www.niic.nsc.ru>.

## References

- Paschke H, Stueber M, Ziebert C, Bistron M, Mayrhofer P. Composition, microstructure and mechanical properties of boron containing multilayer coatings for hot forming tools. *Surf Coatings Technol.* 2011;205:S24–S28. doi:[10.1016/j.surfcoat.2011.04.097](https://doi.org/10.1016/j.surfcoat.2011.04.097)
- Takai T, Furukawa T, Yamano H. Thermophysical properties of austenitic stainless steel containing boron carbide in a solid state. *Mech Eng J.* 2021;8(4):20-00540. doi:[10.1299/mej.20-00540](https://doi.org/10.1299/mej.20-00540)
- Drobjaz E, Zimoglyadova T, Gromov V. Electron-beam surfacing wear-resistant coatings, reinforced refractory metal's borides. *Appl Mech Mater.* 2015;698:419–423. doi:[10.4028/www.scientific.net/AMM.698.419](https://doi.org/10.4028/www.scientific.net/AMM.698.419)
- Orsulova T, Palcek P, Kudelcik J. Effect of plastic deformation on the magnetic properties of selected austenitic stainless steels. *Prod Eng Arch.* 2017;14(14):15–18. doi:[10.30657/pea.2017.14.04](https://doi.org/10.30657/pea.2017.14.04)
- Tanhaei S, Gheisari K, Zaree S. Effect of cold rolling on the microstructural, magnetic, mechanical, and corrosion properties of AISI 316L austenitic stainless steel. *Int J Miner Metall Mater.* 2018;25(6):630–640. doi:[10.1007/s12613-018-1610-y](https://doi.org/10.1007/s12613-018-1610-y)
- Roos S, Rännar E. Process window for electron beam melting of 316LN stainless steel. *Metall.* 2021;11(1):137. doi:[10.3390/met11010137](https://doi.org/10.3390/met11010137)
- Gur'ev A, Lygdenov B, Gur'ev M. Borirovanie malouglerodistoy stali (Boriding of mild steel). M: Moscow, Russia; 2015. 141 p. Russian.
- Bushueva E, Turlo Y, Khamgushkeeva G. Influence of chromium concentration on corrosion resistance of surface layers of stainless steel. In: International Russian-Kazakhstan Conference Chemical Technologies of Functional Materials (RKFМ–2021). 2021;340:7. doi:[10.1051/mateconf/202134001022](https://doi.org/10.1051/mateconf/202134001022)
- Wang S, Yu X, Zhang J, He D, Zhao Y. Crystal structures, elastic properties, and hardness of high-pressure synthesized CrB<sub>2</sub> and CrB<sub>4</sub>. *J Superhard Mater.* 2014;36(4):279–287. doi:[10.3103/S1063457614040066](https://doi.org/10.3103/S1063457614040066)
- Vasil'cov V, Galushkin M, Il'ichev I. Layer-by-layer laser cladding of metal powders: analytical theory and experiment. *Vestnik MGTU im. NJe Baumana.* 2012;6(6):24–26. Russian. doi:[10.18698/2308-6033-2012-6-227](https://doi.org/10.18698/2308-6033-2012-6-227)
- Keddām M, Kul'ka M. Modeling the kinetics of boriding steel AISID2 using two different approaches. *Metalloved Term Obrabotka Metall.* 2019;12:13–20. Russian. doi:[10.30906/mitom.2019.12.13-20](https://doi.org/10.30906/mitom.2019.12.13-20)
- Filonenko N. The physical and thermodynamic functions of borides. *Phys Chem Solid State.* 2017;18(1):58–63. doi:[10.15330/pcss.18.1.58-63](https://doi.org/10.15330/pcss.18.1.58-63)
- Basak S, Sahu K, Sharm S, Majumdar J. Studies on electron beam surface melting of AISI 316 stainless steel and AISI 347 stainless steel. *Proced Manuf.* 2016;7:647–653. doi:[10.1016/j.promfg.2016.12.096](https://doi.org/10.1016/j.promfg.2016.12.096)
- Drobjaz E, Golkovskiy M, Chakin I. Corrosion resistance of materials obtained by electron-beam surfacing by Fe-Cr-Ni-Ti powder mixtures. *Metall Term Obrabotka Metall.* 2021;12:48–53. Russian. doi:[10.30906/mitom.2021.12.48-53](https://doi.org/10.30906/mitom.2021.12.48-53)
- Bushueva E, Grinberg B, Bataev V, Drobjaz E. Raising the resistance of chromium-nickel steel to hydroabrasive wear by non-vacuum electron-beam cladding with boron. *Metal Sci Heat Treat.* 2019;60(9):641–644. doi:[10.1007/s11041-019-00331-3](https://doi.org/10.1007/s11041-019-00331-3)
- Emurlaev K, Golkovskij M, Stepanov N, Bataeva Z. Structure and properties of surface layers obtained by the method of non-vacuum electron-beam surfacing by powder mixtures of copper and boron. *Metall.* 2021;11:62–68. Russian. doi:[10.52351/00260827\\_2021\\_11\\_62](https://doi.org/10.52351/00260827_2021_11_62)
- Malinina E, Goevaya L, Buzanova G, Avdeeva V, Efimova N, Kuznetsov N. A new method for synthesis of binary borides with desired properties. *Chem.* 2019;487(2):180–183. doi:[10.1134/S0012500819070061](https://doi.org/10.1134/S0012500819070061)
- Karaimchuk E, Masljuk V, Mamonova A, Umerova S. Phase-structure formation and features of the behavior of powder materials "iron-high-carbon ferrochromium-nickel boride" under abrasive wear conditions. *Izvestiya Vuzov.* 2020;1:55–64. Russian. doi:[10.17073/1997-308X-2020-55-64](https://doi.org/10.17073/1997-308X-2020-55-64)
- Soyama J, Zepón G, Lopes T, Beraldo L. Microstructure formation and abrasive wear resistance of a boron-modified superduplex stainless steel produced by spray forming. *J Mater Res.* 2016;31(19):2987–2993. doi:[10.1557/JMR.2016.323](https://doi.org/10.1557/JMR.2016.323)
- Koga G, Jorge A, Roche V, Nogueira R. Production and corrosion resistance of thermally sprayed Fe-based amorphous coatings from mechanically milled feedstock powders. *Metall Mater Trans A.* 2018;49(10):4860–4870. doi:[10.1007/s11661-018-4785-y](https://doi.org/10.1007/s11661-018-4785-y)
- Ye L, Wei Y, Shi X, Li Y, Shi Q. Study on W-rich M<sub>3</sub>B<sub>2</sub> borides in a 9Cr<sub>3</sub>W<sub>3</sub>CoB heat-resistant steel. *J Mater Res Technol.* 2021;10:594–604. doi:[10.1016/J.JMRT.2021.05.004](https://doi.org/10.1016/J.JMRT.2021.05.004)
- Wei X. First-principles investigation of Cr-doped Fe<sub>2</sub>B: Structural, mechanical, electronic and magnetic properties. *J Magn Magn Mater.* – 2018;456:150–159. doi:[10.1016/j.jmmm.2018.02.004](https://doi.org/10.1016/j.jmmm.2018.02.004)
- Koga G, Otani L, Silva A, Roche V. Characterization and corrosion resistance of boron-containing-austenitic stainless steels produced by rapid solidification techniques. *Mater.* 2018;11(11):2189. doi:[10.3390/ma11112189](https://doi.org/10.3390/ma11112189)
- Krylova T, Ivanov K, Chumakov Yu, Trotsenko R. Corrosion and wear resistance of coatings produced by nonvacuum electron beam cladding of refractory carbides on low-carbon steel. *Inorg Mater.* 2020;56(3):328–332. doi:[10.1134/S0020168520030097](https://doi.org/10.1134/S0020168520030097)
- Krylova T, Chumakov Y. Fabrication of Cr-Ti-C composite coating by non-vacuum electron beam cladding. *Mater Lett.* 2020;274:128022. doi:[10.1016/j.matlet.2020.128022](https://doi.org/10.1016/j.matlet.2020.128022)
- Baranova A, Konstantinova M, Guseva E, Grechneva M. Intergranular corrosion of austenitic steels. *Sistem Metod Tehnol.*

2015;2:142-147. Russian. Available from:  
<https://www.elibrary.ru/item.asp?id=23599020&ysclid=14tjis190g57936900>, Accessed on 1 June 2022.